

## Packing density and filling effect of limestone fines

A.K.H. Kwan\* and M. McKinley

*Department of Civil Engineering, The University of Hong Kong, Hong Kong*

*(Received October 30, 2013, Revised April 24, 2014, Accepted May 9, 2014)*

**Abstract.** The use of limestone fines (LF) in mortar and concrete can in certain ways improve performance and thus has become more and more commonplace. However, although LF is generally regarded as a filler, it is up to now not clear how much filling effect it could have and how best the filling effect could be utilized. Herein, the packing density and filling effect of LF were studied by measuring the packing densities of LF, (LF + cement) blends and (LF + cement + fine aggregate) blends under dry and wet conditions, and measuring the performance of mortars made with various amounts of LF added. It was found that the addition of LF would not significantly increase the packing density of (LF + cement) blends but would fill into the paste to increase the paste volume and paste film thickness, and improve the flow spread and strength of mortar.

**Keywords:** fillers; limestone fines; mortar; packing density; paste film thickness

---

### 1. Introduction

In recent years, various kinds of fillers, such as limestone fines (LF), have been used in the production of concrete (Bonavetti *et al.* 2003; Mňahončáková *et al.* 2008; Craeye *et al.* 2010). Depending on the fineness of the fillers and how the fillers are added (whether replacing aggregate, cement or cement paste), the addition of fillers has significant effects on the fresh and hardened properties of concrete. Unlike supplementary cementitious materials, which take part in chemical reactions to produce gel for strength development, fillers are chemically inert and thus would not take part in any chemical reactions (Sprung and Siebel 1991). Nevertheless, it has been found that the incorporation of LF in certain ways can enhance the workability, stability and early strength of concrete (Kanazawa *et al.* 1992).

The use of LF in concrete has been a major research topic for many years. LF was first used as an aggregate to replace part of the sand. Malhotra and Carette (1985) observed that replacing part of the sand with LF could increase or decrease the compressive strength of concrete, depending on the water/cement ratio and LF content. Besides, they found that the incorporation of LF would increase the cohesiveness of the fresh concrete and the drying shrinkage of the hardened concrete but has little effect on the durability of the concrete structure.

Later, LF was used to replace part of the cement. Nehdi *et al.* (1996) showed that replacing part of the cement with LF up to 10% or 15% would not affect the early strength of mortar, but would

---

\*Corresponding author, E-mail: khkwan@hku.hk









Table 4 Packing density results of (LF+OPC) blends

Mix no.	LF/OPC ratio	Packing density under each testing condition			Increase in packing density due to presence of water (%)	Increase in packing density due to addition of SP (%)
		D0	W0	W5		
LF+OPC-0.0	0.0	0.448	0.587	0.605	31.0	3.1
LF+OPC-0.2	0.2	0.449	0.592	0.609	31.8	2.9
LF+OPC-0.4	0.4	0.451	0.595	0.612	31.9	2.9
LF+OPC-0.6	0.6	0.454	0.598	0.614	31.7	2.7
LF+OPC-0.8	0.8	0.455	0.600	0.615	31.9	2.5
LF+OPC-1.0	1.0	0.456	0.601	0.617	31.8	2.7

Table 5 Packing density results of (LF+FA) blends

Mix no.	LF/FA ratio	Packing density under each testing condition			Increase in packing density due to presence of water (%)	Increase in packing density due to addition of SP (%)
		D0	W0	W5		
LF+FA-0.0	0.0	0.517	0.619	0.627	19.7	1.3
LF+FA-0.1	0.1	0.536	0.653	0.683	21.8	4.6
LF+FA-0.2	0.2	0.555	0.676	0.708	21.8	4.7
LF+FA-0.3	0.3	0.564	0.688	0.722	22.0	4.9
LF+FA-0.4	0.4	0.569	0.685	0.721	20.4	5.3
LF+FA-0.5	0.5	0.563	0.679	0.719	20.6	5.9
LF+FA-0.6	0.6	0.552	0.673	0.711	21.9	5.6
LF+FA-0.7	0.7	0.547	0.667	0.706	21.9	5.8
LF+FA-0.8	0.8	0.540	0.661	0.701	22.4	6.1
LF+FA-0.9	0.9	0.536	0.657	0.698	22.6	6.2
LF+FA-1.0	1.0	0.533	0.654	0.692	22.7	5.8

Table 6 Packing density results of (OPC+FA) blends

Mix no.	OPC/FA ratio	Packing density under each testing condition			Increase in packing density due to presence of water (%)	Increase in packing density due to addition of SP (%)
		D0	W0	W5		
OPC+FA-0.0	0.0	0.517	0.619	0.627	19.7	1.3
OPC+FA-0.1	0.1	0.531	0.644	0.678	21.3	5.3
OPC+FA-0.2	0.2	0.540	0.661	0.697	22.4	5.4
OPC+FA-0.3	0.3	0.548	0.672	0.709	22.6	5.5
OPC+FA-0.4	0.4	0.552	0.675	0.716	22.3	6.1
OPC+FA-0.5	0.5	0.556	0.667	0.709	20.0	6.3
OPC+FA-0.6	0.6	0.549	0.661	0.702	20.4	6.2
OPC+FA-0.7	0.7	0.541	0.656	0.696	21.3	6.1
OPC+FA-0.8	0.8	0.535	0.654	0.693	22.2	6.0
OPC+FA-0.9	0.9	0.529	0.651	0.691	23.1	6.1
OPC+FA-1.0	1.0	0.524	0.649	0.688	23.9	6.0

Table 7 Packing density results of (LF+OPC+FA) blends

Mix no.	P/FA ratio	Packing density under each testing condition			Increase in packing density due to presence of water (%)	Increase in packing density due to addition of SP (%)
		D0	W0	W5		
P+FA-0.0	0.0	0.517	0.619	0.627	19.7	1.3
P+FA-0.1	0.1	0.534	0.650	0.681	21.8	4.8
P+FA-0.2	0.2	0.548	0.671	0.703	22.6	4.8
P+FA-0.3	0.3	0.556	0.683	0.719	22.8	5.3
P+FA-0.4	0.4	0.561	0.682	0.717	21.7	5.1
P+FA-0.5	0.5	0.560	0.674	0.715	20.5	6.1
P+FA-0.6	0.6	0.551	0.669	0.707	21.5	5.7
P+FA-0.7	0.7	0.544	0.663	0.702	21.9	5.9
P+FA-0.8	0.8	0.538	0.660	0.698	22.8	5.8
P+FA-0.9	0.9	0.533	0.655	0.696	23.0	6.3
P+FA-1.0	1.0	0.529	0.651	0.691	23.2	6.1

more than sufficient to fill the voids. For testing under condition W0, no SP was added while for testing under conditions W1, W2, W3, W4 and W5, SP was added at dosages of 0.5%, 1.0%, 1.5%, 2.0% and 2.5% respectively by mass of the powder content. No compaction was applied because the wet packing tests were mainly to study the effects of water and SP, not compaction. For non-blended samples, each sample was tested under all the six conditions W0, W1, W2, W3, W4 and W5. This was to study the effects of SP on the wet packing density. For blended samples, each sample was tested under the conditions W0 and W5 only because these tests were mainly to study the effects of blending, not SP dosage.

### 3.2 Part B - Mortar tests

Four mortar mixes were produced for testing. Their cement paste volume (volume of cement plus volume of water) was set constant at 50% while their LF volume was varied among 0%, 4%, 8% and 12% of the mortar volume so as to study the filling effects of LF. The remaining volume of the mortar was the FA volume. In other words, the LF was added to replace an equal volume of FA without changing the cement paste volume. For every mortar mix, the water/cement (W/C) ratio by mass was fixed at 0.50. In terms of quantity per volume of mortar, the OPC content was constant at 609 kg/m<sup>3</sup>, the LF content varied from 0 to 317 kg/m<sup>3</sup>, the FA content varied from 993 to 1307 kg/m<sup>3</sup> and the water content (not including the water in the SP) varied from 291 to 294 kg/m<sup>3</sup>. Details of the mix proportions are presented in Table 8. Each mortar mix was assigned an identification code of M-X-Y, in which M denotes mortar, X denotes the cement paste volume and Y denotes the LF volume.

SP was added to each mortar sample. Since SP is a surface reactant and it is the SP dosage per solid surface area that actually governs the effectiveness of the SP (Wong and Kwan 2008b; Kwan *et al.* 2012), the SP dosage was determined according to the total surface area of the solid particles

in the mortar. Before setting the SP dosage to be used, trial cement paste mixing using different SP dosages was carried out and it was found that the saturation dosage (the dosage beyond which further addition of the SP yields little further increase in flowability) was  $3.7 \times 10^{-5}$  kg/m<sup>2</sup> of the solid surface area. Hence, the SP dosage in terms of liquid mass of SP per solid surface area was set as  $3.7 \times 10^{-5}$  kg/m<sup>2</sup> for all the mortar samples. Converted to dosage per volume of mortar, the SP dosage varied from 11 kg/m<sup>3</sup> for the mortar mix containing no LF to 14 kg/m<sup>3</sup> for the mortar mix containing a LF volume of 12%.

The packing density of the particles in each mortar sample was measured using the wet packing method (Wong and Kwan 2008a; Fung *et al.* 2009; Kwan and Fung 2009), as explained before. In this particular study, the 4 mortar samples tested for their rheological and hardened properties were actually made from 4 different mix proportions of LF, OPC and FA. Hence, the 4 mix proportions of LF, OPC and FA were separately tested for their wet packing densities.

After mixing, each mortar sample was subjected to the mini slump cone test and mini V-funnel test for evaluation of its flow ability in terms of flow spread and flow rate. Both the mini slump cone and mini V-funnel tests for mortar may be regarded as reduced scale versions of the slump and V-funnel tests for concrete. There are several versions of mini slump cone and mini V-funnel with different dimensions. The versions adopted here are the same as those used by Okamura and Ouchi (2003). The detailed test procedures have been given before and are therefore not repeated here (Kwan *et al.* 2010).

After the above flow ability tests, the mortar sample was remixed in the mixer and then used to cast six 100 mm cubes, three of which were for testing of 7-day compressive strength and the other three were for testing of 28-day compressive strength. The cubes were cast in steel moulds, covered with a plastic sheet on each top surface and then stored in the laboratory at a temperature of  $24 \pm 2^\circ\text{C}$ . At one day after casting, the moulds were removed and the cubes were cured in a lime-saturated water tank controlled at a temperature of  $27 \pm 2^\circ\text{C}$  until the ages of 7 days and 28 days for cube compression tests.

Table 8 Mix proportions, packing density, WFT and PFT results of mortar samples

Mix no.	Materials content in the mortar (kg/m <sup>3</sup> )					Packing density	WFT ( $\mu\text{m}$ )	PFT ( $\mu\text{m}$ )
	OPC	LF	FA	Water	SP			
M-50-0	609	0	1307	294	11	0.720	0.111	32.7
M-50-4	609	106	1202	293	12	0.717	0.087	42.7
M-50-8	609	211	1098	292	13	0.710	0.054	54.6
M-50-12	609	317	993	291	14	0.705	0.032	69.0

Table 9 Flowability and strength results of mortar samples

Mix no.	Flow spread (mm)	Flow rate (ml/s)	7-day cube strength (MPa)	28-day cube strength (MPa)
M-50-0	60	98	50.5	58.7
M-50-4	75	73	51.2	59.5
M-50-8	65	38	52.9	61.3
M-50-12	50	40	56.5	62.7



## 4. Experimental results

### 4.1 Packing densities of non-blended LF and OPC

Table 2 presents the dry packing density results of the non-blended LF and OPC under the testing conditions D0, D10, D20, D30, D40 and D50 while Table 3 presents the wet packing density results of the non-blended LF and OPC under the testing conditions W0, W1, W2, W3, W4 and W5. From these results, it is obvious that the packing density of the LF was generally within 0.461 to 0.621 whereas the packing density of OPC was generally within 0.448 to 0.605. On the whole, the packing density of LF was higher than the packing density of OPC under any testing condition. This was because the LF has a wider size range than OPC. It is also obvious that for both LF and OPC, the effects of compaction, water and SP are significant.

Comparing the packing density results under the dry conditions D0, D10, D20, D30, D40 and D50, it is evident that under dry condition, the packing density was quite sensitive to the compaction applied. With compaction applied, the dry packing density of LF increased by 3.9%, 6.7%, 8.9%, 11.1% and 11.5% whereas the dry packing density of OPC increased by 2.7%, 6.0%, 8.0%, 11.2% and 12.7%, as the number of compactive blows increased from 0 to 10, 20, 30, 40 and 50, respectively.

Comparing the packing density results under the wet conditions to those under the dry conditions, it is clear that for both LF and OPC, the wet packing density was substantially higher than the dry packing density. With no compaction applied and no SP added, the wet packing densities of LF and OPC were 32.5% and 31.0% higher than the respective dry packing densities. In fact, for both LF and OPC, the wet packing density with no compaction applied and no SP added was at least 16% higher than the respective dry packing density with 50 compactive blows applied.

Comparing the packing density results under the wet conditions W0, W1, W2, W3, W4 and W5, it can be seen that the wet packing density increased slightly with the SP dosage. For LF, the wet packing density increased by up to 1.6% when the SP dosage was increased to 1.0% and thereafter remained the same when the SP dosage was further increased. For OPC, the wet packing density increased by up to 3.1% when the SP dosage was increased to 1.5% and thereafter remained the same when the SP dosage was further increased. Hence, for each material, there was a saturation SP dosage beyond which further increase in SP dosage has little effect. From the above results, the saturation SP dosages for LF and OPC may be determined as 1.0% and 1.5% by mass of the powder content, respectively.

### 4.2 Packing densities of LF+OPC, LF+FA, OPC+FA and LF+OPC+FA blends

Tables 4, 5, 6 and 7 present the packing density results of the (LF+OPC) blends, (LF+FA) blends, (OPC+FA) blends and (LF+OPC+FA) blends under the testing conditions D0, W0 and W5. These results reveal that under the dry condition D0, the packing densities of the LF+OPC, LF+FA, OPC+FA and LF+OPC+FA blends were generally within 0.448 to 0.456, 0.517 to 0.569, 0.517 to 0.556 and 0.517 to 0.561, respectively. Under the wet condition W0 with no SP added, the packing densities of the LF+OPC, LF+FA, OPC+FA and LF+OPC+FA blends were generally within 0.587 to 0.601, 0.619 to 0.688, 0.619 to 0.675 and 0.619 to 0.683, respectively. Under the wet condition W5 with SP added, the packing densities of the LF+OPC, LF+FA, OPC+FA and LF+OPC+FA blends were generally within 0.605 to 0.617, 0.627 to 0.722, 0.627 to 0.716 and

0.627 to 0.719, respectively.

Comparing the packing density results under the wet condition W0 to those under the dry condition D0, it can be seen that for all the blended samples, regardless of the LF/OPC ratio and P/FA ratio, the wet packing density was substantially higher than the corresponding dry packing density. Such effect of water may be evaluated in terms of the increase in packing density due to the presence of water, as tabulated in the respective sixth column in Tables 4, 5, 6 and 7. From the tabulated values, it is evident that the increase in packing density due to the presence of water varied from 19.7% when there was only FA to 31.9% when there was only powder (LF+OPC).

Comparing the packing density results under the condition W5 with SP added to those under the condition W0 with no SP added, it can be seen that for all the blended samples, regardless of the LF/OPC ratio and P/FA ratio, the wet packing density was slightly higher with SP added. Such effect of SP may be evaluated in terms of the increase in packing density due to the addition of SP, as tabulated in the respective seventh column of Tables 4, 5, 6 and 7. As can be seen from the tabulated values, the increase in packing density due to the addition of SP varied from 1.3% to 6.3%. It should be noted that the SP dosage under condition W5 was higher than the saturation SP dosage and thus these increases in packing density are already the best results that could be obtained by the type of SP used.

In theory, blending of different size particles together so that the smaller size particles would fill into the voids between the larger size particles would increase the packing density. However, the actual increase in packing density due to blending is dependent on several factors, including the mix proportions and size ratios of the different size particles blended together. In this research, the opportunity was taken to study the effects of blending under the dry and wet conditions. For this purpose, the packing densities of LF+OPC are plotted against the LF/OPC ratio in Fig. 2 and the packing densities of LF+FA, OPC+FA and LF+OPC+FA are plotted against the P/FA ratio ( $P = \text{LF+OPC}$ ) in Fig. 3.

The curves plotted in Figure 2 reveal that as the LF/OPC ratio increased, the packing density increased only marginally, indicating that blending of OPC with LF has little effect on the packing density. This was because the OPC and LF have similar particle sizes and thus very little filling effect could take place. The marginal increase in packing density with the LF/OPC ratio was due to the slight higher packing density of LF rather than any filling effect of LF.

The curves plotted in Figure 3 reveal that as the P/FA ratio increased from 0 to 1.0, the packing density first increased from the packing density of FA to a maximum packing density at an optimum P/FA ratio and then decreased to the packing density of the powder P (P could be LF, OPC or LF+OPC). The increase in packing density as the P/FA ratio increased from zero to an optimum value was caused by the smaller size P particles filling into the voids between the larger size FA particles (this is exactly the filling effect). The decrease in packing density as the P/FA ratio further increased to beyond the optimum value was caused by the excess P (the portion of P in excess of that needed to fill the voids between the FA particles) pushing the FA particles apart to reduce the solid concentration of FA.

More importantly, the maximum packing density was always higher than both the packing density of FA and the packing density of P, indicating that blending of FA with P could increase the packing density. For instance, under the condition W0, blending of FA with LF, OPC and LF+OPC had increased the packing density by 11.1%, 9.0% and 10.3%, respectively. Comparing the effect of blending on the packing density of LF+OPC and the effect of blending on the packing density of P+FA, it is obvious that the blending of FA with P has a much larger effect than the blending of

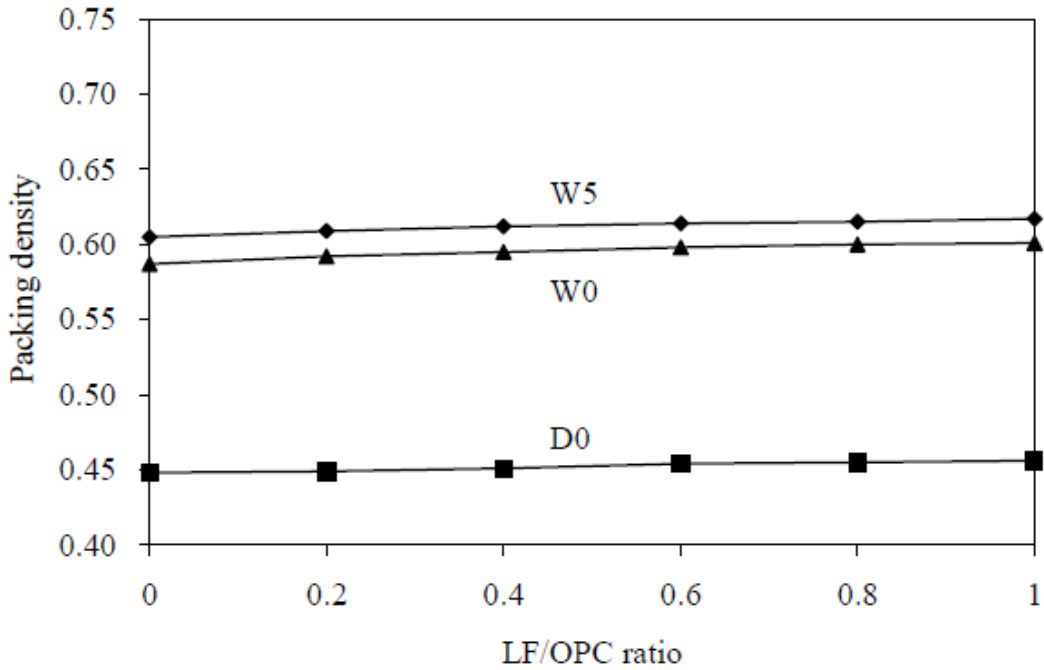


Fig. 2 Packing densities of (LF+OPC) blends

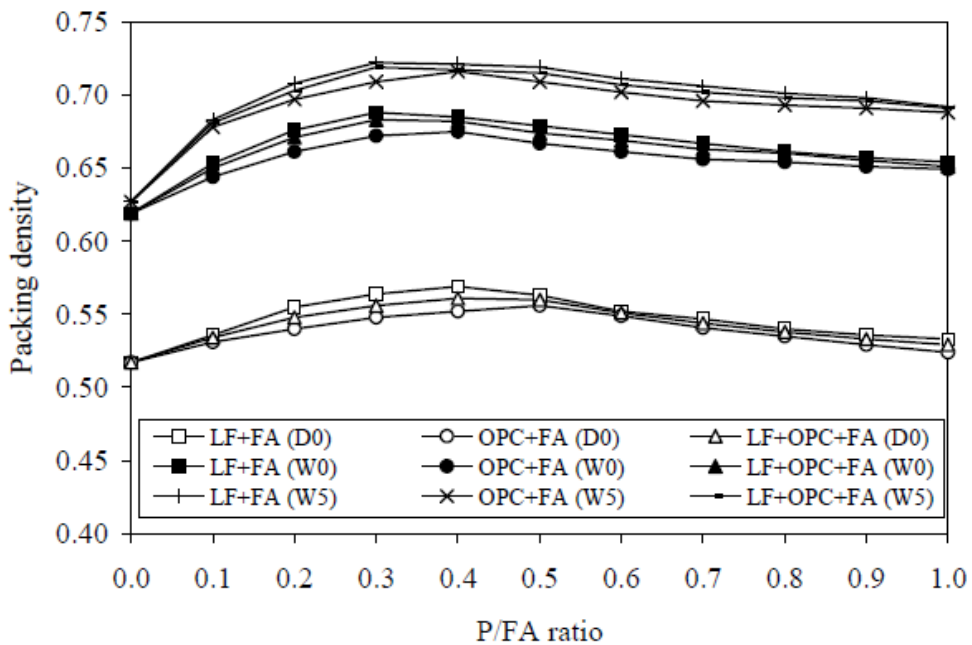


Fig. 3 Packing densities of (LF+FA), (OPC+FA) and (LF+OPC+FA) blends

OPC with LF. This was because of the difference in size ratio (ratio of the size of smaller particles to the size of larger particles). LF and OPC have similar particle sizes and thus the size ratio is close to 1 whereas P is much smaller than FA and thus the size ratio is relatively small. As explained by De Larrard (1999), a smaller size ratio would lead to a larger beneficial effect of blending whereas a larger size ratio would lead to a smaller beneficial effect of blending. This agrees with the general observation that a larger size range would yield a higher packing density.

The curves in Figure 3 also reveal that the optimum P/FA ratio at which the maximum packing density would be achieved was different under different testing conditions. For instance, for the OPC+FA blends, the optimum P/FA ratios under conditions D0, W0 and W5 were 0.5, 0.4 and 0.4, respectively. Hence, the presence of water could affect the optimum P/FA ratio for maximum packing density. Generally, the optimum P/FA ratio was slightly lower under wet condition than dry condition.

#### *4.3 Packing density, water film thickness and paste film thickness of mortar*

The packing density results of the 4 mortar mixes tested are tabulated in the seventh column of Table 8. These results show that the packing density decreased slightly from 0.720 to 0.705 as the LF volume increased from 0% to 12%. This phenomenon can be explained using the packing theory (De Larrard 1999). When the powder volume is small, the powder would fill into the voids between the aggregate particles to increase the packing density, but when the powder volume is large, the powder would become more than enough to fill the voids and the excess powder (the powder in excess of that needed to fill the voids between the aggregate particles) would push the aggregate particles apart thus causing the packing density to decrease. The maximum packing density occurs when the powder is just enough to fill the voids. From Tables 6 and 7, it can be seen that under condition W5, the maximum packing densities of OPC+FA and LF+OPC+FA blends were 0.716 and 0.719, respectively, but in the case of mortar mix M-50-0 with only OPC added and no LF added, the packing density was already as high as 0.720. With the packing density already at maximum, the addition of LF to the mortar would increase the powder content to more than enough to fill the voids, and thus cause the packing density to decrease.

Apart from changing the packing density of the particle system, the addition of a filler like LF would also change the characteristics of the water-solid mixture because of the corresponding changes in voids volume and solid surface area. From previous research (Kwan and Wong 2008b; Fung and Kwan 2010; Kwan and Li 2012), it has been found that the two major characteristics of cement paste and cement-sand mortar governing their fresh and hardened properties are the water film thickness (WFT) and paste film thickness (PFT). The WFT, which has the physical mean of average thickness of water films coating the solid particles, may be determined as the ratio of the excess water (water in excess of that needed to fill the voids between solid particles) to the solid surface area of all solid particles. Likewise, the PFT, which has the physical meaning of average thickness of paste films coating the aggregate particles, may be determined as the ratio of the excess paste to (paste in excess of that needed to fill the voids between aggregate particles) to the solid surface area of aggregate particles.

The WFT was obtained by first measuring the packing density of all solid particles, from which the voids volume (bulk volume minus solid volume) and the excess water volume (water volume minus voids volume) could be evaluated, and then determining the WFT as the excess water to solid surface area of all solid particles ratio. Likewise, the PFT was obtained by first measuring the packing density of the aggregate particles and then determining the PFT as the excess paste to

solid surface area of aggregate particles ratio. However, the FA contained a significant portion of fines (particles smaller than  $75\ \mu\text{m}$ ), which tends to intermix with the OPC, LF and water to form part of the paste. Hence, the paste volume was taken as the total volume of OPC, LF, fines in the FA and water, and the packing density and solid surface area were taken as those of the FA with the fines content excluded by sieving.

The WFT and PFT of the 4 mortar mixes, which all had a constant cement paste volume of 50% and a constant W/C ratio of 0.50, are listed in the last two columns of Table 8 and plotted against the LF volume in Figs. 4 and 5. The WFT results reveal that for the mortar samples tested, the WFT decreased steadily from  $0.111\ \mu\text{m}$  to  $0.032\ \mu\text{m}$  as the LF volume increased from 0% to 12%. This was because the addition of LF had slightly decreased the packing density and significantly increased the solid surface area of the mortar mixes. On the other hand, the PFT results reveal that for the mortar samples tested, the PFT increased steadily from  $32.7\ \mu\text{m}$  to  $69.0\ \mu\text{m}$  as the LF volume increased from 0% to 12%. This was because the addition of LF had significantly increased the paste volume (the paste volume includes the LF volume), had not changed the packing density of the aggregate and had decreased the solid surface area of the aggregate (due to decrease in aggregate content as part of the aggregate had been replaced by the LF added).

Summarizing, the addition of LF without changing the cement paste volume and W/C ratio would slightly decrease the packing density, significantly decrease the WFT and significantly increase the PFT. These are due to the corresponding changes in powder content, paste volume, aggregate content, solid surface area of all solid particles and solid surface area of aggregate particles. The filling effect of limestone fines is now clear. Although limestone fines has been regarded as a filler and even called limestone filler for many years, the actual filling effect of LF has never been thoroughly investigated. For the particular type of LF used herein, which has similar fineness as OPC, it has no filling effect when added to OPC to form a (LF+OPC) blend but has some filling effect when added to FA to form a (LF+FA) blend. When added to OPC and FA to form a (LF+OPC+FA) blend, it would increase the packing density if the OPC/FA ratio is less than the optimum for maximum packing density but would decrease the packing density if the OPC/FA

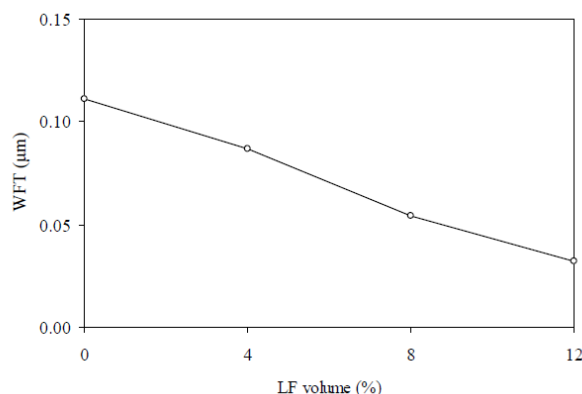


Fig. 4 Effect of LF on WFT of mortar

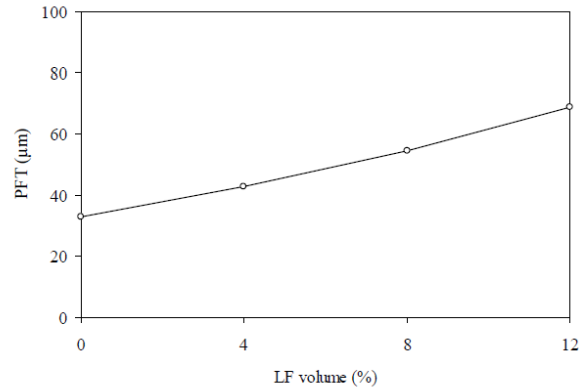


Fig. 5 Effect of LF on PFT of mortar

ratio is higher than the optimum for maximum packing density. When added to a mortar without changing the cement paste volume and W/C ratio, it would decrease the WFT and increase the PFT. Overall, it may be said that the filling effect of LF is contributed main by the LF filling into the paste to increase the paste volume and PFT.

#### 4.4 Flowability of mortar

The flow spread and flow rate results are listed in Table 9 and plotted against the LF volume in Figs. 6 and 7. These results indicate very clearly that the addition of LF has significant effects on the flowability of mortar.

From the flow spread results, it can be seen that the flow spread first increased as the LF volume increased and then after reaching a maximum value at a LF volume of 4%, started to decrease as the LF volume further increased. Among the 4 mortar mixes tested, the mortar mixes with LF volumes of 4% and 8% have larger flow spread than the mortar mix with no LF added whereas the mortar mix with a LF volume of 12% has a smaller flow spread than the mortar mix

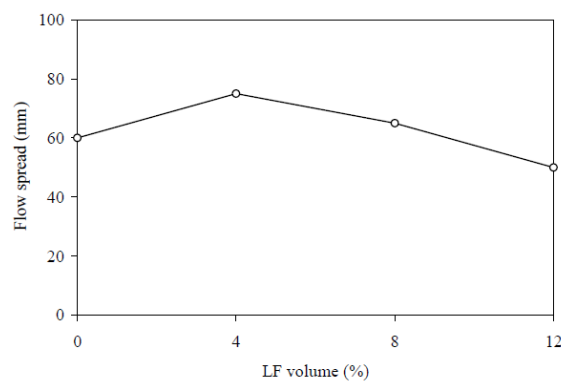


Fig. 6 Effect of LF on flow spread of mortar

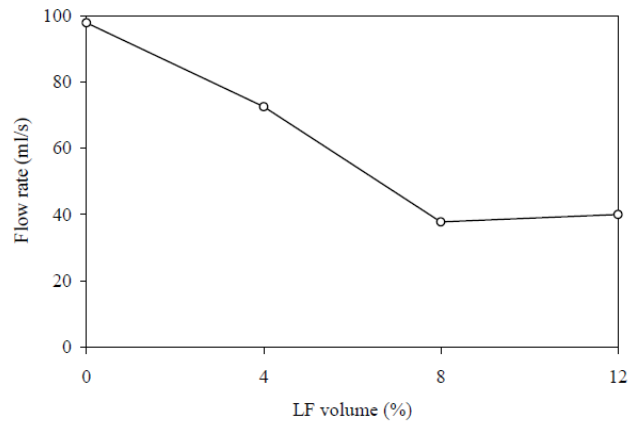


Fig. 7 Effect of LF on flow rate of mortar

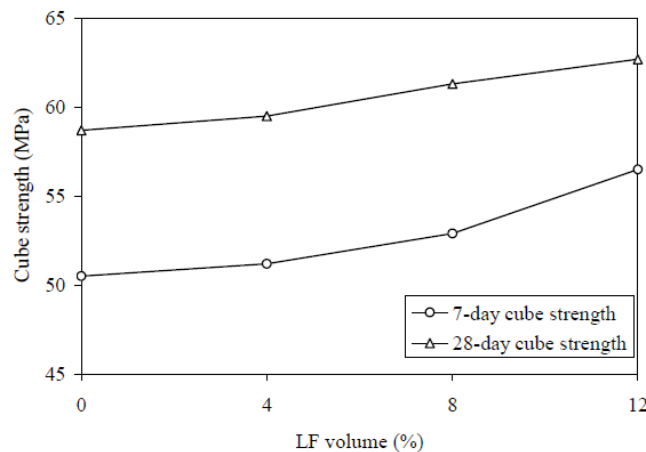


Fig. 8 Effect of LF on cube strength of mortar

with no LF added. Such variation of the flow spread with the LF volume may be attributed to the combined effects of the corresponding changes in WFT and PFT. Whilst the decrease in WFT due to addition of LF should have caused the flow spread to decrease, the concurrent increase in PFT due to addition of LF should have caused the flow spread to increase. It is quite likely that the effect of WFT is larger when the WFT is relatively small and smaller when the WFT is relatively large. Likewise, it is likely that the effect of PFT is larger when the PFT is relatively small and smaller when the PFT is relatively large. While the LF volume was smaller than 4%, the WFT was relatively large and the PFT was relatively small; in such situation, the PFT should have larger effect than the WFT and as a result, the flow spread increased as the LF volume increased. While the LF volume was larger than 4%, the WFT was relatively small and the PFT was relatively large; in such situation, the WFT should have larger effect than the PFT and as a result, the flow spread decreased as the LF volume further increased.

From the flow rate results, it can be seen that the flow rate decreased as the LF volume increased and then after reaching a certain value at a LF volume of 8%, remained more or less constant as the LF volume further increased. All the mortar mixes containing LF have smaller flow rate than the mortar mix containing no LF. In other words, the addition of LF would in general decrease the flow rate of mortar. Again, such variation of the flow rate with the LF volume may be attributed to the combined effects of the corresponding changes in WFT and PFT. Previous research (Kwan and Li 2012) has shown that for the flow rate of mortar, the WFT generally has larger effect than the PFT. So, it was the decrease in WFT as the LF volume increased that caused the flow rate to decrease with increase in LF volume.

#### *4.5 Cube strength of mortar*

The 7-day and 28-day cube strength results are tabulated in the last two columns of Table 9 and plotted against the LF volume in Fig. 8. Each cube strength result presented therein is the average of the three cubes cast from the same batch and tested at the same time. These results show that the cube strength increased slightly as the LF volume increased. With no LF added, the 7-day and 28-day cube strengths attained were 50.5 MPa and 58.7 MPa, respectively. With 12% LF added, the 7-day and 28-day cube strengths increased to 56.5 MPa (an increase of 11.9%) and 62.7 MPa (an increase of 6.8%), respectively. Hence, although the LF is chemically inert and would not react with the cement and water to produce gel, its addition to mortar can increase the early strength by up to 12% and the long term strength by up to 7%. This may be attributed to the decrease in the WFT, which reduces bleeding and thus improves the bond between aggregate particles and hardened cement paste, and the nucleation effect of the fine LF particles, which promotes precipitation of gel products and thus enhances the hydration of cement. The increase in PFT may also have certain positive effect because a larger PFT would allow easier compaction of the mortar mix during casting.

## **5. Conclusions**

To study the effects of LF on the packing densities of the powder content and the whole particle system in mortar, the wet packing method has been applied to measure the packing densities of non-blended LF, and (LF + cement), (LF + fine aggregate) and (LF + cement + fine aggregate) blends. For comparison, the materials were also tested by the dry packing method with and without compaction applied. From the test results, it is evident that the wet packing density even with no compaction applied is generally much higher than the respective dry packing density with compaction applied and that the addition of superplasticizer could significantly increase the wet packing density. The test results of the (LF + cement) blends revealed that blending of cement with LF would not significantly increase the packing density because the LF has similar particle size as the cement whereas the test results of the (LF + fine aggregate) and (LF + cement + fine aggregate) blends revealed that blending of fine aggregate with LF or with both LF and cement could significantly increase the packing density because the LF and cement particles are much smaller than the aggregate particles and are thus able to fill into the voids between the aggregate particles. However, the effects of blending revealed by the wet packing test are not the same as those revealed by the dry packing test. Since the particles in mortar are actually under wet condition when freshly mixed, the wet packing test should be more appropriate for studying the



effects of LF.

On the other hand, the mortar test results showed that for the particular mortar mixes tested with a constant cement paste volume of 50% and a constant W/C ratio of 0.5, the addition of LF would slightly decrease the packing density, significantly decrease the water film thickness (WFT) and significantly increase the paste film thickness (PFT). The slight decrease in packing density was because the addition of LF had caused the powder content to be more than enough to fill the voids between aggregate particles and the aggregate particles to be pushed apart. The decrease in WFT was caused by the slight decrease in packing density and the increase in solid surface area of all solid particles due to the addition of LF. The increase in PFT was caused by the increase in paste volume and the decrease in solid surface area of aggregate particles. The filling effect of LF is now clear. For a LF, which has similar fineness as cement, it has no filling effect when added to cement to form a (LF + cement) blend. It also has no filling effect when added to a mortar mix in which the powder content is already enough to fill the voids between aggregate particles. Its filling effect is contributed mainly by the LF filling into the paste to increase the paste volume and PFT.

Lastly, the flow spread and flow rate results revealed that the addition of LF could increase the flow spread but would decrease the flow rate of mortar. These were due to the corresponding changes in WFT and PFT. Hence, it is incorrect to simply say whether the addition of LF would improve or impair the flowability of mortar or concrete. Under static or near static condition such as ordinary placing of concrete, the flow spread is more important and thus the addition of LF may be advantageous. But under dynamic condition such as concrete pumping, the flow rate is more important and thus the addition of LF is not considered advisable. Regarding the cube strength results, the addition of LF without changing the W/C ratio could increase the 7-day and 28-day cube strengths by about 12% and 7%, respectively. It should be noted however that the LF added was not cementitious and thus should not have chemically reacted with the cement or water. The increases in strength may be attributed to the decrease in the WFT, which reduces bleeding and thus improves the bond between aggregate particles and hardened cement paste, and the nucleation effect of the fine LF particles, which promotes precipitation of gel products and thus enhances the hydration of cement. The increase in PFT may also have certain positive effect because a larger PFT would allow easier compaction of the mortar mix during casting.

## References

- Bentz, D.P. (2005), "Replacement of "coarse" cement particles by inert fillers in low w/c ratio concretes; II: experimental validation", *Cement Concrete Res.*, **35**(1), 185-188.
- Bentz, D.P. and Conway, J.T. (2001), "Computer modeling of the replacement of "coarse" cement particles by inert fillers in low w/c ratio concretes: hydration and strength", *Cement Concrete Res.*, **31**(3), 503-506.
- Bentz, D.P., Irassar, E.F., Bucher, B. and Weiss, W.J. (2009), "Limestone fillers conserve cement in low w/cm concretes; an analysis based on Powers' model", *Concrete Int.*, **31**(11), 41-46.
- Bonavetti, V., Donza, H., Menéndez, G., Cabrera, O. and Irassar, E.F. (2003), "Limestone filler cement in low w/c concrete: a rational use of energy", *Cement Concrete Res.*, **33**(6), 865-871.
- British Standards Institution (1995), *BS 812-2: 1995. Testing Aggregates: Methods of Determination of Density*. British Standards Institution, UK.
- British Standards Institution (1998), *BS EN 1097-3: 1998. Tests for Mechanical and Physical Properties of Aggregates: Determination of Loose Bulk Density and Voids*. British Standards Institution, UK.
- British Standards Institution (2000), *BS EN 197-1: 2000. Cement Composition, Specifications and Conformity Criteria for Common Cements*. British Standards Institution, UK.

- British Standards Institution (2005), *BS EN 196-1: 2005. Methods of Testing Cement: Determination of Strength*. British Standards Institution, UK.
- British Standards Institution (2008), *BS EN 1097-4: 2008. Tests for Mechanical and Physical Properties of Aggregates: Determination of the Voids of Dry Compacted Filler*. British Standards Institution, UK.
- British Standards Institution (2010), *BS EN 196-6: 2010. Methods of Testing Cement. Determination of Fineness*. British Standards Institution, UK.
- Chen, J.J. and Kwan, A.K.H. (2012), "Adding limestone fines to reduce heat generation of curing concrete", *Mag. Concrete Res.*, **64**(12), 1101-1111.
- Craeye, B., de Schutter, G., Desmet, B., Vantomme, J., Heirman, G., Vandewalle, L., Cizer, Ö., Aggoun, S. and Kadri, E.H. (2010), "Effect of mineral filler type on autogenous shrinkage of self-compacting concrete", *Cement Concrete Res.*, **40**(6), 908-913.
- De Larrard, F. (1999), *Concrete Mixture Proportioning: A Scientific Approach*. E & FN Spon, New York, USA.
- Diederich, P., Mouret, M., de Ryck, A., Ponchon, F. and Escadeillas, G. (2012), "The nature of limestone filler and self-consolidating feasibility - relationships between physical, chemical and mineralogical properties of fillers and the flow at different states, from powder to cement-based suspension", *Powder Tech.*, **218**, 90-101.
- Fung, W.W.S. and Kwan, A.K.H. (2010), "Role of water film thickness in rheology of CSF mortar", *Cement Concrete Compos.*, **32**(4), 255-264.
- Fung, W.W.S., Kwan, A.K.H. and Wong, H.H.C. (2009), "Wet packing of crushed rock fine aggregate", *Mater. Struct.*, **42**(5): 631-643.
- Kanazawa, K., Yamada, K. and Sogo, S. (1992), "Properties of low-heat generating concrete containing large volumes of blast-furnace slag and fly ash", *Fly Ash, Silica Fume, Slag, and Natural Pozzolans in Concrete, ACI Special Publication SP-132*, American Concrete Institute, USA, 97-118.
- Kwan, A.K.H., Chen, J.J. and Fung, W.W.S. (2012), "Effects of superplasticiser on rheology and cohesiveness of CSF cement paste", *Adv. Cement Res.*, **24**(3), 125-137.
- Kwan, A.K.H. and Fung, W.W.S. (2009), "Packing density measurement and modelling of fine aggregate and mortar", *Cement Concrete Compos.*, **31**(6), 349-357.
- Kwan, A.K.H., Fung, W.W.S. and Wong, H.H.C. (2010), "Water film thickness, flowability and rheology of cement-sand mortar", *Adv. Cement Res.*, **22**(1), 3-14.
- Kwan, A.K.H. and Li, L.G. (2012), "Combined effects of water film thickness and paste film thickness on rheology of mortar", *Mater. Struct.*, **45**(9), 1359-1374.
- Kwan, A.K.H., McKinley, M. and Chen, J.J. (2013), "Adding limestone fines as cement paste replacement to reduce shrinkage of concrete", *Mag. Concrete Res.*, **65**(15), 942-950.
- Kwan, A.K.H. and Wong, H.H.C. (2008a), "Packing density of cementitious materials: part 2 - packing and flow of OPC + PFA + CSF", *Mater. Struct.*, **41**(4), 773-784.
- Kwan, A.K.H. and Wong, H.H.C. (2008b), "Effects of packing density, excess water and solid surface area on flowability of cement paste", *Adv. Cement Res.*, **20**(1), 1-11.
- Lee, S.H., Kim, H.J., Sakai, E. and Daimon, M. (2003), "Effect of particle size distribution of fly ash-cement system on the fluidity of cement pastes", *Cement Concrete Res.*, **33**(5), 763-768.
- Malhotra V.M. and Carette G.G. (1985) "Performance of concrete incorporating limestone dust as partial replacement for sand", *J. Am. Concrete Inst.*, **82**(3), 363-371.
- Mňahončáková, E., Pavlíková, M., Grzeszczyk, S., Rovnaníková, P. and Černý R. (2008), "Hydric, thermal and mechanical properties of self-compacting concrete containing different fillers", *Construct. Build. Mater.*, **22**(7), 1594-1600.
- Nanthagopalan, P., Haist, M., Santhanam, M. and Müller, H.S. (2008), "Investigation on the influence of granular packing on the flow properties of cementitious suspensions", *Cement Concrete Compos.*, **30**(9), 763-768.
- Nehdi, M., Mindess, S. and Aitcin, P.C. (1996), "Optimization of high strength limestone filler cement mortars", *Cement Concrete Res.*, **26**(6), 883-893.
- Okamura, H. and Ouchi, M. (2003), "Self-compacting concrete", *J. Adv. Concrete Tech.*, **1**(1), 5-15.

- Opczky L. (1992), "Progress of particle size distribution during the intergrinding of a clinker-limestone mixture", *Zement-Kalk-Gips*, **45**(12), 648-651.
- Soroka, I. and Setter, N. (1977), "The effect of fillers on strength of cement mortars", *Cement Concrete Res.*, **7**(4), 449-456.
- Sprung, S. and Siebel, E. (1991), "Assessment of the suitability of limestone for producing Portland limestone cement (PKZ)", *Zement-Kalk-Gips*, **44**(1), 1-11.
- Svarovsky, L. (1987), *Powder Testing Guide: Methods of Measuring the Physical Properties of Bulk Powders*. Elsevier Applied Science Publishers Ltd, UK.
- Wong, H.H.C. and Kwan, A.K.H. (2008a), "Packing density of cementitious materials: part 1 - measurement using a wet packing method", *Mater. Struct.*, **41**(4), 689-701.
- Wong, H.H.C. and Kwan, A.K.H. (2008b), "Rheology of cement paste: role of excess water to solid surface area ratio", *J. Mater. Civil Eng.*, **20**(2), 189-197.