

# Effect of fly ash and plastic waste on mechanical and durability properties of concrete

Gopal Paliwal\* and Savita Maru<sup>a</sup>

*Department of Civil Engineering, Ujjain Engineering College, Ujjain (M.P.), India*

*(Received August 9, 2017, Revised September 13, 2017, Accepted September 21, 2017)*

**Abstract.** The disposal of polythene waste and fly ash is causing serious threat to the environment. Aim of this study is to decrease environmental pollution by using polythene waste and fly ash in concrete. In this study, cement was partially replaced with 0%, 5%, 10%, 15% and 20% fly ash (by weight) and plastic waste was added in shredded form at 0.6% by weight of concrete. The specimens were prepared for the concrete mix of M25 grade and water to cementitious material ratio (w/c) was maintained as 0.45. Fresh concrete property like workability was examined during casting the specimens. Hardened properties were found out by carrying out the experimental work on cubes, cylinders and beams which were cast in laboratory and their behavior under test were observed at 7 & 28 days for compressive strength and at 28 days for density, flexural strength, dynamic modulus of elasticity, abrasion resistance, water permeability and impact resistance.

Overall results of this study show that addition of 0.6% (by weight of the concrete) plastic waste with 10% (by weight of cement) replacement of cement by fly ash result an improvement in properties of the concrete than conventional mix.

**Keywords:** fly ash; plastic waste; workability; density; compressive strength; flexural strength; dynamic modulus of elasticity; abrasion resistance; water permeability; impact resistance

---

## 1. Introduction

Concrete is a composite material incorporate cement, sand, aggregate, water and admixture. Concrete is the 2<sup>nd</sup> most largely used material in the world after water. In India, 370 million m<sup>3</sup> concrete is being utilized by construction industries per year and it is anticipated to broaden 30 million m<sup>3</sup> every year. Also, origins of all basic ingredients of concrete are nature, which are reducing with increase in consumption of concrete due to popular growth of construction industry. Therefore, it is require finding alternate material which can be utilized in the production of concrete. The revolutionary in construction industry called green concrete, which is produced by adopting the waste.

The production of plastic waste and fly ash has been increasing at an alarming rate, disposal of which has become a serious environmental problem. In this study an attempt is made to utilize

---

\*Corresponding author, PG Student, E-mail: [gopalkpaliwal@gmail.com](mailto:gopalkpaliwal@gmail.com)

<sup>a</sup>Ph.D.



Table 1 Physical properties of cement

Sr. No.	Properties	Test results
1	Consistency	32%
2	Initial setting time	130 minutes
	Final setting time	213 minutes
3	Specific gravity	3.13
4	7-day compressive strength	34.95 MPa
5	28-day compressive strength	45.29 MPa

## *2.2 Fine aggregate*

The fine aggregate used for investigation belongs to the zone II, was procured from the local fine aggregate suppliers and conform all requirements as per IS: 383-1970. The specific gravity test was performed in the laboratory and value achieved was 2.63.

## *2.3 Coarse aggregates*

Coarse aggregate of 10 mm and 20 mm sizes were used in this study and they conform all requirements as per IS: 383-1970. It was free from dust particles, vegetation, organic matters and clay. The specific gravity test was performed in the laboratory and value achieved was 2.78.

## *2.4 Water*

Ordinary water available in the laboratory was used in this investigation both for mixing and curing the concrete specimens throughout the investigation and it conform all requirements as per IS: 456-2000.

## *2.5 Plastic waste (polythene bags)*

The plastic wastes used in this study were consisting waste polythene bags in shredded form. Bags did not be given any special treatment except the normal water wash, cleaning and day light drying and then cut into plastic shredding machine to achieve shredded form. Specific gravity test was performed in laboratory and value achieved was 0.33.

## *2.6 Fly ash*

Class F fly ash collected from Shree Singaji Thermal Power Project, Khandwa, Madhya Pradesh was used during the experiment. Specific gravity test was performed in the laboratory and value achieved was 2.5.

## **3. Methodology**

The methodology adopted to accomplish the objective of the experimental investigation and execution of work was done in step by step as follows:



*Effect of fly ash and plastic waste on mechanical and durability properties of concrete*

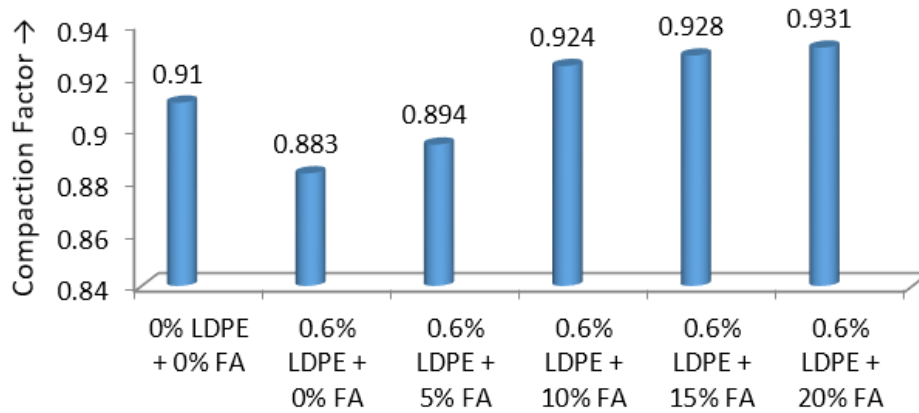


Fig. 1 Variation of compaction factor with fly ash content

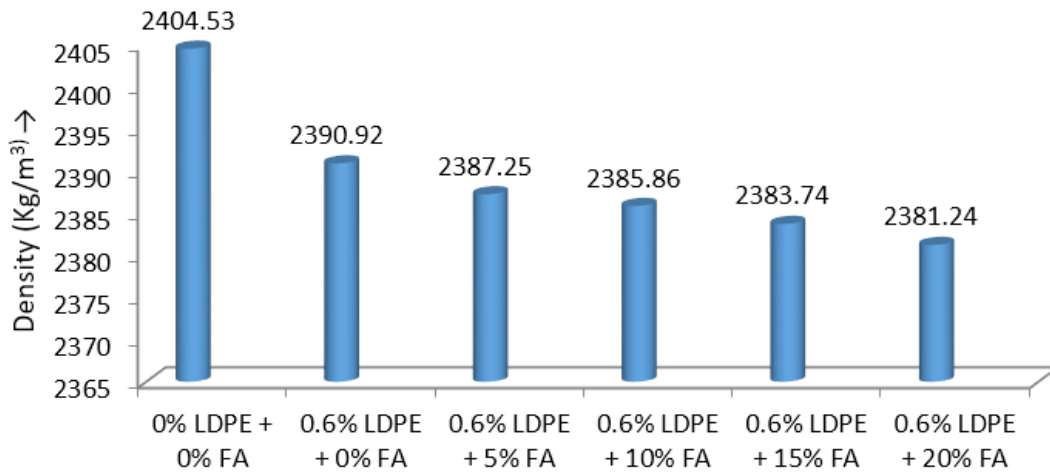


Fig. 2 Variation of density with fly ash content

#### 4. Results and discussion

Here discussion on results of tests carried out in the laboratory to investigate the various properties such as workability, density, compressive and flexural strength, modulus of elasticity, abrasion resistance, water permeability and impact resistance is done to analyze the data obtained.

##### 4.1 Workability

Compaction factor test was used for determining the workability of fresh concrete. Bar chart has been plotted for variation of compaction factor with percentage fly ash as shown in Fig. 1. Compaction factor value of control mix is achieved as 0.91 which reduced to 0.883 for 0.6% plastic waste addition to the control mix. On replacing 10% of cement by fly ash in plastic waste containing concrete, compaction factor value increases to 0.924. A general trend observed is increment in compaction factor with increase in fly ash content up to 10% dosage. Hence till 10% fly ash dose workability gets enhanced.



*Effect of fly ash and plastic waste on mechanical and durability properties of concrete*

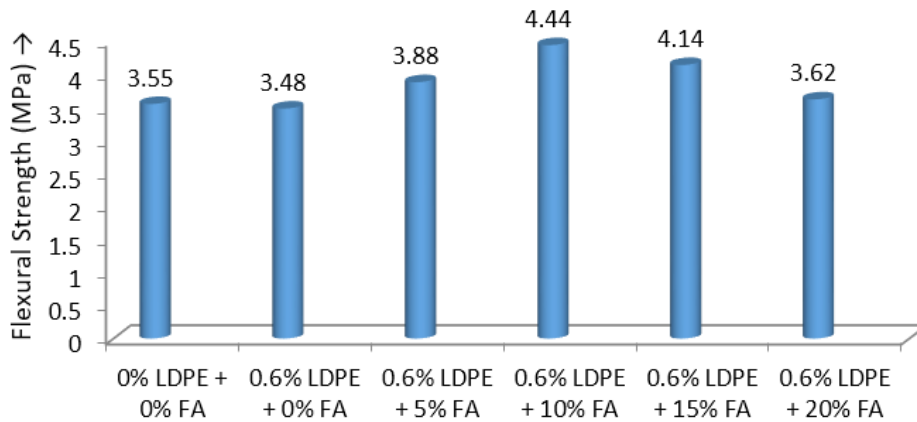


Fig. 4 Variation of flexural strength with fly ash content

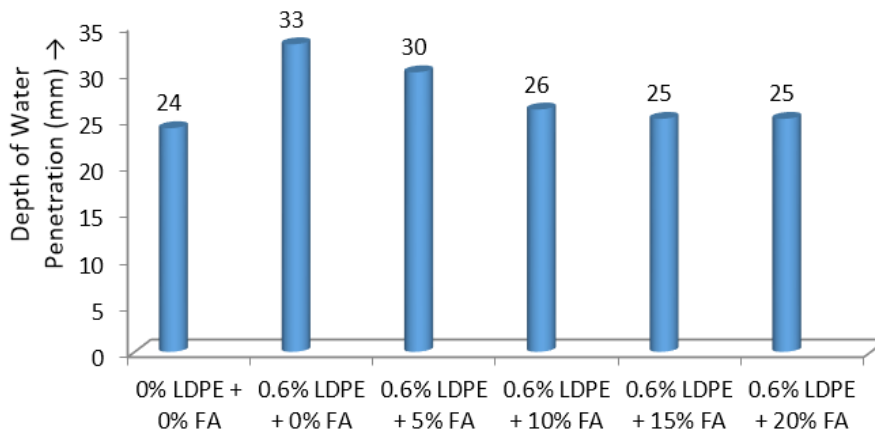


Fig. 5 Variation of depth of water penetration with fly ash content

increase in fly ash results decrease in strength value, although strength value achieved is more than that of control mix. Thus, replacement of cement by fly ash gives positive and improved results than that with cement only. Most probable cause of improvement in the strength may be due to reaction of fly ash with lime, released during hydration of cement, which produces additional binders to give additional strength.

#### *4.5 Water permeability*

Fig. 5 shows variation of water penetration depth with % fly ash. The trend recorded for the variation of water penetration depth with fly ash dose is that the depth of water penetration decreases as fly ash percentage increases. Depth of water penetration is considerably decreased till 10% and then it almost remains at same value.

The decrease in penetration of water may be due to refinement of pore structure as fly ash is more efficient void filler than OPC. Additional cementitious material results from reaction between surplus lime (liberated from hydration of cement) and fly ash, blocks capillary voids and thereby reduces permeability of concrete.

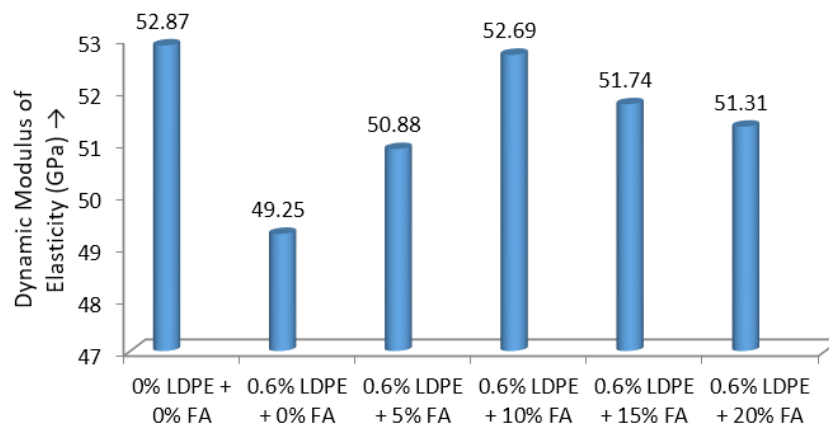


Fig. 6 Variation of dynamic modulus of elasticity with fly ash content

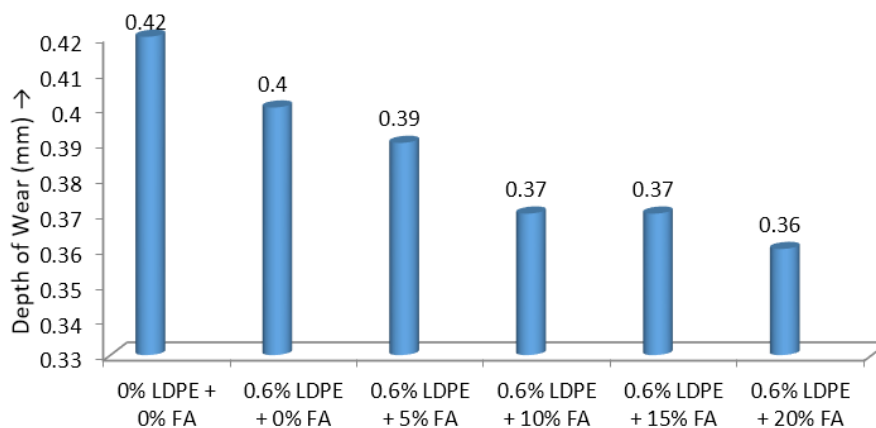


Fig. 7 Variation of depth of wear due to abrasion with fly ash content

#### 4.6 Dynamic modulus of elasticity

Variation of dynamic modulus of elasticity with fly ash can be observed in Fig. 6 that with increment in fly ash content it increases up to 10% dose. After 10% dose decrement is observed in dynamic modulus of elasticity. Thus, 10% fly ash content gives maximum dynamic modulus of elasticity value.

Ultrasonic pulses travel with higher velocity through uniform concrete. As addition of fly ash results better packing of concrete matrix and uniformity. So, velocity of ultrasonic pulses increases, which might result increase in dynamic modulus of elasticity.

#### 4.7 Abrasion resistance

Variation of wear depth due to abrasion with percentage fly ash content is as shown in Fig. 7. The results indicated that the abrasion resistance of concrete increased with addition of plastic waste, i.e., less wear of depth is observed when 0.6% of shredded plastic bag is added into the concrete mix than the control mix. Also by replacing cement to various percentages by fly ash,



*Effect of fly ash and plastic waste on mechanical and durability properties of concrete*

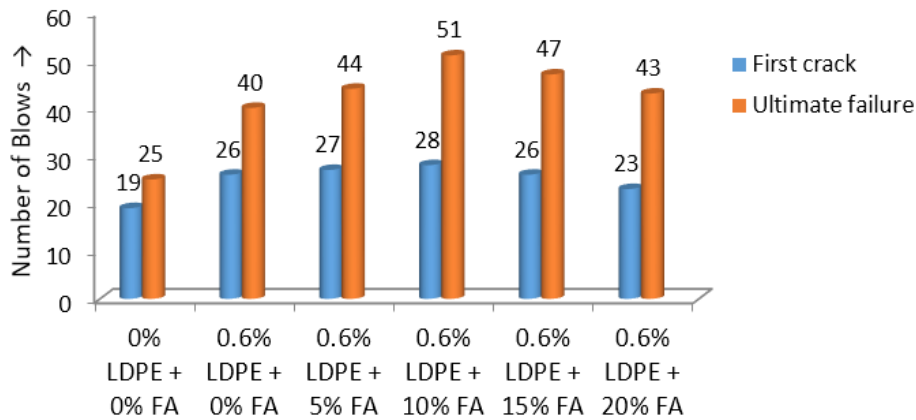


Fig. 8 Variation of number of blows required for first & ultimate cracks with fly ash content

wear depth decreased continuously. Thus, a better abrasion resistance is observed when fly ash is present in the concrete along with plastic waste.

Improved packing effect of matrix by filling up of micro pores with fly ash might be the reason of increased resistance to abrasion in concrete containing plastic waste with fly ash.

#### *4.8 Impact resistance*

The impact resistance was determined with drop weight test. The impact resistance of concrete mixes (average of three specimens for each mix) at 28 days curing was recorded in terms of numbers of blows required for producing first visible crack ( $N_1$ ) and ultimate failure ( $N_2$ ) of the specimen and their variation with fly ash percentage is presented in bar chart as shown in Fig. 8.

It can be observed from the graph that the number of blows required for causing the first crack and ultimate failure increased for shredded plastic bag reinforced concrete mix than control mix. Further addition of fly ash to this mix resulted into increase in number of blows for both first crack and ultimate failure up to 10% dosage of fly ash. After 10% fly ash, impact strength started decreasing, although it is more than that of control mix.

Better packing of concrete matrix due to less availability of pores and better binding of ingredients in the concrete mix may be the cause of improvement of impact strength.

## **5. Conclusions**

The main aim of this study was to investigate the possibility of using shredded polythene waste materials and fly ash as concrete ingredients. Fresh and hardened properties like workability, density, compressive strength, flexural strength, water permeability, abrasion resistance, dynamic modulus of elasticity and impact resistance were examined in laboratory for concrete specimens containing plastic waste and fly ash. Following conclusions can be drawn after comparing the results:

- The 10% replacement of cement by fly ash improved the workability, compressive strength and flexural strength of the concrete containing 0.6% (by weight of concrete) polythene waste by 2.3%, 7.7% and 25% of conventional mix respectively.

- The density of concrete containing 0.6% (by weight of concrete) polythene waste decreased with increase in the percentage of fly ash up to 10% by weight of cement. After which any further addition of fly ash results in a small density decrease. The decrease in density at 10% fly ash content is about 0.97% of that for conventional mix.
- The dynamic modulus of elasticity decreased by 6.9% of conventional mix when 0.6% (by weight of concrete) polythene waste added. But 10% replacement of cement by fly ash in the concrete containing plastic waste increased the dynamic modulus of elasticity by about 6.9%.
- The water permeability of concrete containing 0.6% (by weight of concrete) polythene waste increased by 37% of conventional mix. When 10% of cement was replaced by fly ash in the concrete containing plastic waste, depth of penetration decreased by about 25%. Thus, improved the water permeability through by decreasing the depth of penetration.
- Replacement of 10% of cement by fly ash results decrease in depth of wear by 12% of conventional mix. The abrasion resistance of concrete containing 0.6% (by weight of concrete) polythene waste increased as the amount of fly ash increased up to 10% by weight of cement. After which the wear depth became almost constant for any further increase in fly ash.
- The number of blows required for first crack and ultimate crack for concrete with 10% fly ash content were increased by 47.4% and 104% of conventional mix respectively. Thus, impact resistance of concrete containing 0.6% (by weight of concrete) polythene waste increased with increase in the percentage of fly ash up to 10% by weight of cement.
- Based on results it can be concluded that polythene waste and fly ash can be used as ingredients in concrete. Fresh and hardened properties of concrete with 0.6% plastic waste (by weight of concrete) were improved when 10% cement was replaced by fly ash (by weight). Due to improved permeability it can be used in construction work at offshore region. This modified concrete can also be used in earthquake prone areas where the impact resistance is most required parameter over strength. Also, it becomes a good option for structures where light weight concrete required as self-weight of concrete decreases due to a decrease in density.

## References

- ACI 544 (1999), *Drop Weight Test*.
- Al-Hadithi, A.I. and Hilal, N.N. (2016), "The possibility of enhancing some properties of self-compacting concrete by adding waste plastic fibers", *J. Build. Eng.*, **8**, 20-28.
- ASTM C597 (2009), *Standard Test Method for Pulse Velocity through Concrete*.
- Bhogayata, A. and Arora, N.K. (2011), "Green concrete from the postconsumer plastic wastes: Indian scenario", *ICTSET Proc.*, 437-440.
- Bhogayata, A., Shah, K.D., Vyas, B.A. and Arora, N.K. (2012), "Performance of concrete by using non-recyclable plastic wastes as concrete constituent", *J. Eng. Res. Technol.*, **1**(4), 1-3.
- Chandrashekar, A., Ravi Shankar, A.U. and Girish, M.J. (2012), "Fatigue behavior of steel fibre reinforced concrete with fly ash", *Highw. Res. J.*, 9-15.
- Chethan, C. and Chandershekar, A. (2015), "Experimental study on effect of addition of fly ash on the properties of plastic fibers reinforced concrete", *J. Res. Appl. Sci. Eng. Technol.*, **21**(7), 1486-1491.
- DIN 1048 (1991), *Water Permeability Test*.
- Fly ash for Cement Concrete: Resource for High Strength and Durability of Structures at Lower Cost, *Ash Utilization Division NTPC Limited A-11*.
- Frigione, M. (2010), "Recycling of PET bottles as fine aggregate in concrete", *Waste Manage.*, **30**(6), 1101-1106.
- Garg, C. and Jain, A. (2014), "Green concrete: Efficient and eco-friendly construction materials", *J. Res.*

*Effect of fly ash and plastic waste on mechanical and durability properties of concrete*

*Eng. Technol.*, **2**(2), 259-264.

- Gawande, A., Zamare, G., Renge, V.C., Tayde, S. and Bharsakale, G. (2012), "An overview on waste plastic utilization in asphaltting of roads", *J. Eng. Res. Stud.*, **3**(2), 1-5.
- Ghernouti, Y., Rabehi, B., Safi, B. and Chaid, R. (2011), "Use of recycled plastic bags waste in the concrete", *J. Sci. Publ. Mater. Meth. Technol.*, 480-487.
- Halit, Y. (2008), "The effect of silica fume and high-volume class C fly ash on mechanical properties, chloride penetration and freeze–thaw resistance of self-compacting concrete", *Constr. Build. Mater. Sci. Dir.*, **22**(4), 456-462.
- IS 10262 (2009), *Indian Standard Recommended Guidelines for Concrete Mix Design*.
- IS 1199 (1959), *Methods of Sampling and Analysis of Concrete*.
- IS 1237 (2012), *Cement Concrete Flooring Tiles-Specification*.
- IS 2383 Part-1 (1963), *Methods of Test for Aggregates for Concrete*.
- IS 3812 Part 1 (2003), *Pulverized Fuel Ash-Specification; for Use as Pozzolana in Cement, Cement Mortar and Concrete*.
- IS 3812 Part 2 (2003), *Pulverized Fuel Ash-Specification; for Use as Admixture in Cement Mortar and Concrete*.
- IS 383 (1970), *Indian Standard Specification for Coarse and Fine Aggregates from Natural Sources for Concrete*.
- IS 456 (2000), *Indian Standard, Plain and Reinforced Concrete-Code of Practice*.
- IS 516 (1959), *Methods of Tests for Strength of Concrete*.
- IS 8112 (1989), *43 Grade Ordinary Portland Cement-Specification*.
- Islam, G.S. and Gupta, S.D. (2016), "Evaluating plastic shrinkage and permeability of polypropylene fiber reinforced concrete", *J. Sustain. Built Environ.*, 1-10.
- Ismail, Z.Z. and Al-Hashmi, E.A. (2008), "Use of waste plastic in concrete mixture as aggregate replacement", *Waste Manage.*, **28**(11), 2041-2047.
- Khatib, J.M. (2008), "Performance of self-compacting concrete containing fly ash", *Constr. Build. Mater. Sci. Dir.*, **22**(9), 1963-1971.
- Jayeshkumar, P., Zala, L.B. and Umrigar, F.S. (2012), "Experimental investigations on partial replacement of cement with fly ash in design mix concrete", *J. Adv. Eng. Technol.*, **5**(3), 126-129.
- Kandasamy, R. and Murugesan, R. (2011), "Fibre reinforced concrete using domestic waste plastic fibers", *APSN J. Eng. Appl. Sci.*, **6**(3).
- Kumar, A., Srivastava, V. and Kumar, R. (2014), "Effect of waste polythene on compressive strength of concrete", *J. Acad. Industr. Res.*, **3**(3), 152.
- Kumar, K.B.V. and Prakash, P. (2006), "Use of waste plastic in cement concrete pavement", *Adv. Mater. Res. J.*, **15**, 1-21.
- Liu, F., Yan, Y., Li, L., Lan, C. and Chen, G. (2013), "Performance of recycled plastic-based concrete", *J. Mater. Civil Eng.*, **27**(2), 1-9.
- Berndt, M.L. (2009), "Properties of sustainable concrete containing fly ash, slag and recycled concrete aggregate", *Constr. Build. Mater.*, **23**(7), 2606-2613.
- Malak, K.R. (2015), "Use of waste plastic in concrete mixture as aggregate replacement", *J. Eng. Edu. Technol.*, **3**(2).
- Marthong, C. and Sarma, D.K. (2015), "Influence of PET fiber geometry on the mechanical properties of concrete: An experimental investigation", *Eur. J. Environ. Civil Eng.*, **20**(7), 771-784.
- Marzouk, O.Y., Dheilily, R.M. and Queneudec, M. (2007), "Valorization of post-consumer waste plastic in cementitious concrete composites", *Waste Manage.*, **27**(2), 310-318.
- Moinul Islam, M. and Saiful Islam, M. (2010), "Strength behavior of mortar using fly ash as partial replacement of cement", *Concrete Res. Lett.*, **1**(3), 98-106.
- Mody, P. and Mihu, R. (2012), "Curses of plastic on environment", *Asian J. Res. Soc. Sci. Human.*, **2**(1), 55-60.
- Bouzoubaa, N. and Lachemi, M. (2001), "Self-compacting concrete incorporating high volumes of class F fly ash preliminary results", *Cement Concrete Res.*, **31**, 413-420.

- Naik, T.R., Singh, S.S., Huber, C.O. and Brodersen, B.S. (1996), "Use of post-consumer waste plastics in cement-based composites", *Cement Concrete Res.*, **26**(10), 1489-1492.
- Nibudey, R.N., Nagarnaik, P.B., Parbat, D.K. and Pande, A.M. (2013), "Cube and cylinder compressive strengths of waste plastic fiber reinforced concrete", *J. Civil Struct. Eng.*, **4**(2), 1818-1825.
- Patil, P.S., Mali, J.R., Tapkire, G.V. and Kumavat, H.R. (2014), "Innovative techniques of waste plastic used in concrete mixture", *J. Res. Eng. Technol.*, **3**(9), 29-32.
- Patil, S.L., Kale, J.N. and Suman, S. (2012), "Fly ash concrete: A technical analysis for compressive strength", *J. Adv. Eng. Res. Stud.*, **2**(1), 128-129.
- Pilato, L. (2010), *Phenolic Resins: A Century of Progress*, New York, Springer.
- Prahallada, M.C. and Prakash, K.B. (2013), "Effect of addition of flyash on the properties of waste plastic fibre reinforced concrete-an experimental investigation", *J. Sci. Eng. Technol.*, **2**(2), 87-95.
- Prinya, C., Chai, J. and Theerawatt, S. (2005), "Effect of fly ash fineness on compressive strength and pore size of blended cement paste", *Cement Concrete Compos.*, **27**(4), 425-428.
- Rafat, S. (2011), "Properties of self-compacting concrete containing class F fly ash", *Mater. Des.*, **32**(3), 1501-1507.
- Raghatate Atul, M. (2012), "Use of plastic in a concrete to improve its properties", *J. Adv. Eng. Res. Stud.*, **1**(3), 109-111.
- Rahmani, E., Dehestani, M., Beygi, M.H.A., Allahyari, H. and Nikbin, I.M. (2013), "On the mechanical properties of concrete containing waste PET particles", *Constr. Build. Mater.*, **47**, 1302-1308.
- Rai, B., Rushad, S.T., Kr, B. and Duggal, S.K. (2012), "Study of waste plastic mix concrete with plasticizer", *ISRN Civil Eng.*, 1-5.
- Ravina, D. and Mehta, P.K. (1986), "Properties of fresh concrete containing large amounts of fly ash", *Cement Concrete Res.*, **16**(2), 227-238.
- Sabarinathan, A. and Suresh, S. (2016), "An investigation on fresh and hardened properties of M30 concrete with plastic fibres and m-sand", *J. Res. Innovat. Eng. Technol.*, **2**(12), 64-69.
- Saikia, N. and De Brito, J. (2012), "Use of plastic waste as aggregate in cement mortar and concrete preparation: A review", *Constr. Build. Mater.*, **34**, 385-401.
- Saikia, N. and De Brito, J. (2014), "Mechanical properties and abrasion behaviour of concrete containing shredded PET bottle waste as a partial substitution of natural aggregate", *Constr. Build. Mater.*, **52**, 236-244.
- Siddique, R., Khatib, J. and Kaur, I. (2008), "Use of recycled plastic in concrete: A review", *Waste Manage.*, **28**(10), 1835-1852.
- Shetty, M.S. (2013), *Concrete Technology-Theory and Practical*, S. Chand Publishing.
- Trossarelli, L. and Brunella, V. (2003), *Polyethylene: Discovery and Growth*, UHMWPE Meeting, 5-18.
- Usman, M., Javaid, A. and Panchal, S. (2015), "Feasibility of waste polythene bags in concrete", *J. Eng. Trend. Technol.*, **23**(6), 317-319.
- Vidivelli, B. and Mageswari, M. (2010). "Study on fly ash concrete using sem analysis", *J. Environ. Res. Develop.*, **5**(1), 46-52.
- <<http://web.archive.org/web/20170810183511/https://www.slideshare.net/KriveshMK/main-projor-48421439>>.
- <<https://perma.cc/797A-ZVGD>>.
- <<https://perma.cc/9CG3-JSMT>>.
- <<https://perma.cc/CB24-AJN>>.
- <<https://perma.cc/VE3Q-SPQD>>.