

Durability studies on concrete with partial replacement of cement and fine aggregates by fly ash and tailing material

B.M.Sunil^{*}, Manjunatha L.S.^a and Subhash C. Yaragal^b

Department of Civil Engineering, National Institute of Technology, Surathkal, Karnataka, India

(Received July 13, 2017, Revised September 29, 2017, Accepted December 4, 2017)

Abstract. Commonly used concrete in general, consists of cement, fine aggregate, coarse aggregate and water. Natural river sand is the most commonly used material as fine aggregate in concrete. One of the important requirements of concrete is that it should be durable under certain conditions of exposure. The durability of concrete is defined as its ability to resist weathering action, chemical attack or any other process of deterioration. Durable concrete will retain its original form, quality and serviceability when exposed to its environment. Deterioration can occur in various forms such as alkali aggregate expansion, freeze-thaw expansion, salt scaling by de-icing salts, shrinkage, attack on the reinforcement due to carbonation, sulphate attack on exposure to ground water, sea water attack and corrosion caused by salts. Addition of admixtures may control these effects. In this paper, an attempt has been made to replace part of fine aggregate by tailing material and part of cement by fly ash to improve the durability of concrete. The various durability tests performed were chemical attack tests such as sulphate attack, chloride attack and acid attack test and water absorption test. The concrete blend with 35% Tailing Material (TM) in place of river sand and 20% Fly Ash (FA) in place of OPC, has exhibited higher durability characteristics.

Keywords: iron ore tailing; fly ash; compressive strength; chemical attack; durability

1. Introduction

In general, cement is the most important constituent of concrete. Production of cement involves an energy intensive kilning process and causes significant contribution to the green-house gas emission. A single industry accounts for around 5% of global carbon dioxide (CO₂) emissions. To ensure greener construction practice, it is essential to reduce the green-house gas contributions from cement production or to replace cement with other environmentally friendly and efficient by-product materials.

Behera *et al.* (2000), has attempted to develop and use Fly-Ash (FA) in activated form. 20%, 30%, 40% and 50% of Portland cement was replaced by FA. Different physical properties of the cement thus prepared have been examined. It was found that up to 35% FA in activated form can be used for manufacturing blended cement as per Indian Standards (IS 1489: Part 1 2015).

^{*}Corresponding author, Assistant Professor, E-mail: bmsunil@gmail.com

^aResearch Scholar, E-mail: manj.lakkol@gmail.com

^bProfessor, E-mail: subhashyaragal@yahoo.com

and concretes.

This study attempts to ascertain the right potential use of iron ore tailing and fly ash to develop durable concrete with part replacement of fine aggregate TM and part replacement of OPC by fly ash, to study its utilization for construction activity under different environmental conditions.

2. Materials and methods

2.1 Cement

The Ordinary Portland Cement (OPC) of 43 grade confirming to IS: 8112-2013 was used. Table 1 and 2 show the physical and chemical characteristics of cement.

Table 1 Physical properties of cement

Sl. No.	Physical properties of cement	Result	Requirements as per IS: 8112-1989
1	Fineness (m ² /kg)	334	Min 225
2	Specific gravity	3.10	3.10-3.15
3	Normal consistency (%)	29	-
4	Initial setting time (min)	120	Min 30
5	Final setting time (min)	440	Max 600

Table 2 Chemical characteristics of cement

Sl. No.	Properties	Result
1	pH	11.47
2	Electrical conductivity (ms/ μ s)	6.95
3	Silica oxide (SiO ₂) (w/w) %	19.48
4	Iron oxide (Fe ₂ O ₃) (w/w) %	2.00
5	Aluminium oxide (Al ₂ O ₃) (w/w) %	8.25
6	Calcium oxide (CaO) (w/w) %	56.08
7	Magnesium oxide (MgO) (w/w) %	5.64
8	Loss on ignition (%)	4.77

2.2 Tailing material

Mine tailing is one of the waste materials generated from the mining industry and was collected from tailing dam, at Kudremukha, Karnataka, India. Tailing samples were taken at a depth of 0.90 m below the surface in the tailing dam and then transported to the laboratory in sealed bags. In laboratory, the tailing samples were air dried in shade and were then stored in non-corrodible bins for further investigation. From the particle size distribution curve (Fig. 1), it is observed that the fines percentage (silt and clay) is very less (about 5%). Further, it is noticed that the sand proportion is significant (about 95%). From the sieve analysis results, TM satisfied codal requirements confirming to zone III of IS: 383 2016.

2.4 Coarse aggregate

Nominal sizes of coarse aggregates (12.5 mm and 20 mm) as per IS 383-1970 were used in mix design. Table 5 shows the various physical properties of coarse aggregate used in this study.

Table 5 Physical properties of coarse aggregate

Sl. No.	Properties	Coarse aggregate	
		12.5 mm	20 mm
1	Specific gravity	2.75	2.68
2	Fineness modulus	3.23	3.11
3	Water absorption (%)	0.50	0.50
4	Compacted bulk density (kg/m ³)	1550	1420

Table 6 Physical properties and chemical properties of fly ash

Sl. No	Characteristics	Fly Ash
Physical Property		
1	Specific gravity	2.07
2	Fineness (m ² /kg)	290
3	Bulk density (kg/m ³)	1100-1200
4	Colour (Visual observation)	Light grey
Chemical Composition		
5	pH	10.21
6	Calcium oxide (CaO) (w/w) %	10.00
7	Silica oxide (SiO ₂) (w/w) %	72.08
8	Aluminium oxide (Al ₂ O ₃) (w/w) %	5.15
9	Iron oxide (Fe ₂ O ₃) (w/w) %	0.57
10	Magnesium oxide (MgO) (w/w) %	4.04
11	Loss of ignition (%)	0.76

2.5 Fly ash

Fly ash is an industrial byproduct generated from Thermal Power Plants during combustion of coal. Particles are glassy, spherical ball bearings finer than cement particles. Sizes of particle are 0.1 μ m-150 μ m. Fly ash from M/s Raichur Thermal Power Station, Shakthinagar, Karnataka, has been used for the present investigation, which falls under siliceous based fly ash as per IS 3812-2013 (Part-1). Table 6 presents the physical and chemical properties of fly ash.

2.6 Water

Water is an important ingredient of concrete as it actually participates in the chemical reaction with cement. The water used was clean and free from deleterious matter.

Table 9 Mix proportions for fly ash replacement

Sl. No	Mix ID	TM (%)	Sand (%)	Cement (%)	Fly ash (%)	Mix proportion
1	TM35/F0	35	65	100	0	1.00:0:1.68:2.57
2	TM35/F20	35	65	80	20	0.80:0.20:1.64:2.52
3	TM35/F30	35	65	70	30	0.70:0.30:1.63:2.49
4	TM35/F40	35	65	60	40	0.60:0.40:1.61:2.46
5	TM35/F50	35	65	50	50	0.50:0.50:1.59:2.44

sulphate attack and acid attack tests are detailed below,

2.9.1 Water absorption

150 mm concrete cubes were prepared for various mixes and water cured for 28 days. The specimen were then air dried for 24 hours. The dried specimen were weighed accurately to note the dry weight. The dried specimen were immersed in water. Weight of the specimen at pre-determined intervals of time were taken after wiping the surface with dry cloth. This process was continued for not less than 48 hours or up to extent of time till constant weight was obtained in two successive observations.

2.9.2 Sulphate attack

When concrete is exposed to environment containing aggressive chemicals, it leads to deterioration of concrete which can be assessed in terms of loss of weight of concrete. To study the acid resistance of concrete, the cube specimen were cured for 28 days. After 28 days, all specimens were kept in atmosphere for 2 days for constant weight. Subsequently, the specimen were weighed and then immersed in 3% Na_2SO_4 (pH=7, maintained using buffer) solution up to 28 days. After 28 days of immersion, the specimen were taken out and visually observed for the deterioration of the concrete due to sulphate attack. The specimens were weighed once again and the weight is compared with the normal control concrete weight in order to calculate the percentage of loss of weight and also the loss of strength. Figure 2 shows the concrete cubes after sulphate attack.



Fig. 2 Concrete cubes after sulphate attack

3.2 Water absorption

Table 10 shows the average water absorption test results for different blended mixes. A lower water absorption was noted for mixes TM35/F0 and TM35/F20 and a constant higher absorption was noted for the remaining three concrete mixes. This implies that inclusion of 35% TM and less than 20% fly ash will have beneficial effect of reduction in absorption characteristics and consequently enhancing the durability of the concrete. In this regard, FA in controlled amount will be suitable for inclusion in normal concrete. The bar chart in Fig. 5 is a pictorial relationship between water absorption and mix designation.

Table 10 Percentage of water absorption

Sl. No	Mix ID	Average Water Absorption (%)
1	TM35/F0	0.71
2	TM35/F20	0.76
3	TM35/F30	0.92
4	TM35/F40	0.90
5	TM35/F50	0.89

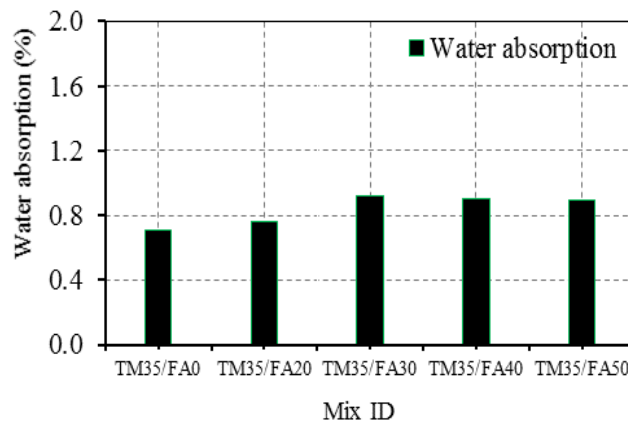


Fig. 5 Variation in water absorption for different blended concrete mixes

3.3 Sulphate attack

Tables 11 and 12 shows the sulphate attack test results of average % loss in weight and % loss in strength of concrete cube specimen for different blended mixes.

As per BS: 8110 Part 1, Clause 6.2.5.3, the total water soluble sulphate content of the concrete mix expressed as SO₃ should not exceed 4% by mass of cement in the mix.

Table 11 shows the percentage loss of weight of tailing and tailing fly ash concrete specimen immersed in sodium sulphate solution. Weight loss of TM35/F50 is not reported as it is not an optimized mix. Fig. 6 shows the loss of weight of the concrete cubes immersed in sodium sulphate solution at various curing periods. From Fig. 6, it is observed that weight losses are lesser in tailing fly ash concrete when compared to the tailing based concrete.

Table 12 shows the increase in strength due to sulphate attack after 56 days immersed in sulphate solution. Fig. 7, shows the percentage increase in strength of concrete cubes immersed in sulphate solution. The blended mix TM35/F20 shows good resistance to sulphate attack than control concrete.

3.4 Acid attack

Tables 13 and 14 show the acid attack test results of average % loss in weight and % loss in strength of concrete cube specimen of control concrete and different blended mixes when immersed in H₂SO₄ solution.

The results of percentage loss in weight of tailing fly ash concrete are shown in Table 13. Also, Fig. 8 shows the loss of weight of the concrete cubes immersed in sulphuric acid (H₂SO₄) solution at various curing periods. From Fig. 8, it is observed that weight losses are lesser in fly ash concrete when compared to the tailing concrete.

Table 13 Percentage loss of weight due to sulphuric acid (H₂SO₄) attack

Sl. No	Mix notation	Average percentage loss of weight		
		Duration of curing (days)		
		7	28	56
1	TM35/F0	3.45	5.65	7.54
2	TM35/F20	3.08	5.48	7.35
3	TM35/F30	2.29	5.48	7.41
4	TM35/F40	1.64	3.93	6.47

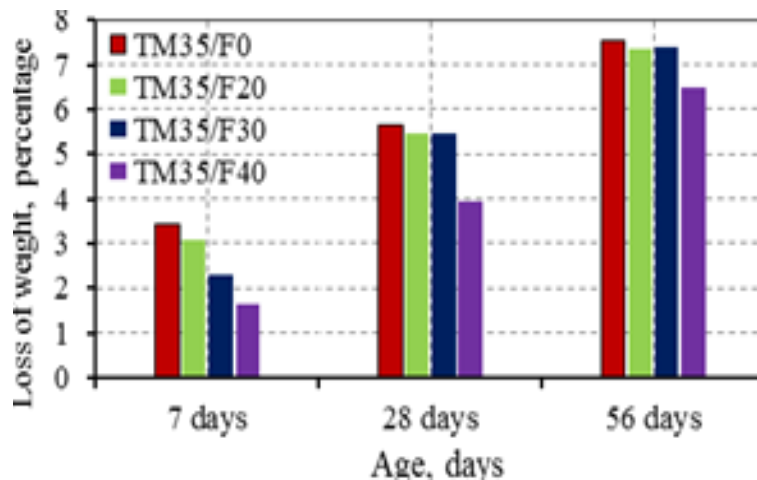
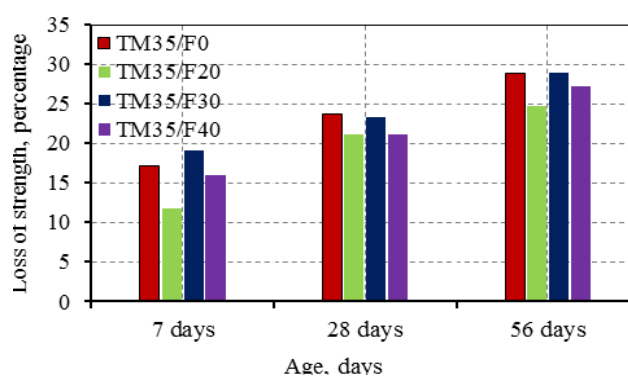


Fig. 8 Percentage loss of weight due to sulphuric acid (H₂SO₄) attack

The test results of loss in strength of tailing fly ash concrete immersed in H₂SO₄ solution are shown in Table 14. It is observed from Table 14 mix TM35/F20 shows good resistance to acid attack when compared with tailing based concrete. The results are also plotted in Fig. 9.

Table 14 Percentage loss of strength due to sulphuric acid (H₂SO₄) attack

Sl. No	Mix notation	Loss of compressive strength (%)		
		Duration of curing (days)		
		7	28	56
1	TM35/F0	17.11	23.72	28.82
2	TM35/F20	11.81	21.12	24.73
3	TM35/F30	19.07	23.24	28.96
4	TM35/F40	15.95	21.12	27.16

Fig. 9 Percentage loss of strength due to sulphuric acid (H₂SO₄) attack

4. Conclusions

The following conclusions were drawn from the study:

- Concrete with 35% TM showed higher compressive strength for 28 days curing. Further additions of TM caused reduction in the strength.
- It is recommended that 35% of TM having compressive strength of 53 MPa, can be used as replacement to river sand in order to obtain concrete with good strength properties.
- The concrete blended with 35% TM and 20% FA has exhibited higher durability characteristics (low water absorption-0.76%, sulphate attack-0.20% and acid attack-5.48%)

References

- Aruna, M. (2012), *Utilization of Iron Ore Tailings in Manufacturing of Paving Blocks for Ecofriendly Mining*, IC-GWBT2012, Ahmad Dahlan University.
- Aruna, M. and Kumar, N.S. (2010), "Studies on iron tailings towards usage for paving blocks manufacture", *J. Earth Sci. Eng.*, **3**(6), 861-868.
- Behera, J.P., Sarangi, B., Nayak, B.D. and Ray, H.S. (2000), "Investigations on the development of blended cement using activated fly ash", *Ind. Concrete J.*, **74**(5), 260-263.
- Bureau of Indian Standards IS 1489: Part 1 (2015), *Portland Pozzolana Cement-Specification Part 1 Fly Ash Based (Fourth Revision)*.
- Escalante-Garcia, J.I. and Sharp, J.H. (2004), "The chemical composition and microstructure of hydration products in blended cements", *Cement Concrete Compos.*, **26**(8), 967-976.

- Huang, X., Ravi R. and Victor, C.L. (2013), "Feasibility study of developing green ECC using iron ore tailings powder as cement replacement", *J. Mater. Civil Eng.*, **25**, 923-931.
- Malhotra, V.M. (1990), "Durability of concrete incorporating high-volume of low-calcium (ASTM class F) fly ash", *Cement Concrete Compos.*, **12**(4), 271-277.
- Mehmood, A.A. and Mulligan, C.N. (2010), "Investigation of the use of mine tailings for unpaved road base", *Wat. Energy*, **12**(1), 106-117.
- Mehta, P.K. (1989), "Pozzolanic and cementitious by-products in concrete: Another look", *ACI Concrete Int.*, **114**, 1-44.
- Ravikumar, C.M., Anilkumar, P.M.H. and Venkat Reddy, D. (2012), "Experimental studies on iron ore taining based interlocking paver blocks", *J. Earth Sci. Eng.*, **5**(3), 501-504.
- Siddique, R. (2004), "Performance characteristics of high-volume Class F fly ash concrete", *Cement Concrete Res.*, **34**(3), 487-493.
- Sunil, B.M., Manjunath, L.S., Lolitha, R. and Subhash, C.Y. (2015), "Potential use of mine tailings and fly ash in concrete", *Adv. Concrete Constr.*, **1**(3), 55-69.
- Yaragal, S.C. and Roshan Muhammad, A.K. (2017), "Usage potential of recycled aggregates in mortar and concrete", *Adv. Concrete Constr.*, **5**(3), 201-219.
- Yaragal, S.C., Teja, D. C. and Shaffi, M. (2016), "performance studies on concrete with recycled coarse aggregates", *Adv. Concrete Constr.*, **4**(4), 263-281.
- Yellishetty, M., Karpe, V., Reddy, E.H., Subhash, K.N. and Ranjith, P.G. (2008), "Reuse of iron ore mineral wastes in civil engineering constructions: A case study", *Res. Conserv. Rec.*, **52**(11), 1283-1289.
- Zhang, S., Xue, X., Liu, X., Duan, P., Yang, H., Jiang, T. and Liu, R. (2006), "Current situation and comprehensive utilization of iron ore tailing resources", *J. Min. Sci.*, **42**(4), 403-408.